

BEYOND STRUCTURE: INVARIANT CRYSTAL PROPERTY PREDICTION WITH PSEUDO-PARTICLE RAY DIFFRACTION

Bin Cao^{1,4}, Yang Liu^{2*}, Longhan Zhang¹, Yifan Wu³, Zhixun Li², Yuyu Luo³, Hong Cheng², Yang Ren^{4*}, Tong-Yi Zhang^{1,5*}

¹Guangzhou Municipal Key Laboratory of Materials Informatics, Advanced Materials Thrust, The Hong Kong University of Science and Technology (Guangzhou)

²The Chinese University of Hong Kong

³Data Science and Analytics Thrust, The Hong Kong University of Science and Technology (Guangzhou)

⁴Department of physics, The City University of Hong Kong

⁵Materials Genome Institute, Shanghai University

ABSTRACT

Crystal property prediction, governed by quantum mechanical principles, is computationally prohibitive to solve exactly for large many-body systems using traditional density functional theory. While machine learning models have emerged as efficient approximations for large-scale applications, their performance is strongly influenced by the choice of atomic representation. Although modern graph-based approaches have progressively incorporated more structural information, they often fail to capture long-term atomic interactions due to finite receptive fields and local encoding schemes. This limitation leads to distinct crystals being mapped to identical representations, hindering accurate property prediction. To address this, we introduce PRDNet that leverages unique reciprocal-space diffraction besides graph representations. To enhance sensitivity to elemental and environmental variations, we employ a data-driven pseudo-particle to generate a synthetic diffraction pattern. PRDNet ensures full invariance to crystallographic symmetries. Extensive experiments are conducted on Materials Project, JARVIS-DFT, and MatBench, demonstrating that the proposed model achieves state-of-the-art performance. The code will be released once our paper is accepted.

1 INTRODUCTION

Material properties are fundamentally determined by quantum mechanical equations such as the Schrödinger equation (Kohn et al., 1996), which are intractable for many-body systems and thus commonly approximated by Density Functional Theory (DFT). However, the high computational cost of DFT limits its application to large atomic systems. Recently, machine learning (ML) force fields have emerged as scalable surrogates (Chen et al., 2019; Chen & Ong, 2022), trained on DFT data to enable efficient structure relaxation and property prediction across diverse materials. These models achieve near-DFT accuracy while allowing exploration of large-scale atomic correlations.

In particular, the performance of ML models strongly depends on how atomic systems are represented (Xie & Grossman, 2018; Schütt et al., 2017; Chen et al., 2019; Louis et al., 2020; Choudhary & DeCost, 2021; Yan et al., 2022; 2024; Taniai et al.; Ito et al., 2025). Early efforts relied on hand-engineered descriptors to capture atomic interactions (Isayev et al., 2017; Su et al., 2024; Zhu et al., 2024), which offered interpretability but suffered from human bias and poor transferability. With the emergence of data-driven models, Graph Neural Networks have become mainstream crystal encoding models. Specifically, they treat crystals as graphs and perform message passing (Chen et al., 2019) to aggregate node information. Initial solutions focus solely on pairwise local interactions, leveraging graph convolution networks (Xie & Grossman, 2018; Chen et al., 2019) and graph attention networks (Louis et al., 2020). To capture higher-order geometry, later works incorporated

*Corresponding authors (yangliu005@cuhk.edu.hk, yangren@cityu.edu.hk, mezhangt@hkust-gz.edu.cn)

atomic angular embedding (e.g., bond angles and multi-body descriptors) (Choudhary & DeCost, 2021; Chen & Ong, 2022), improving structural fidelity but at the expense of efficiency and symmetry invariance. Most recently, equivariant/invariant GNNs (Yan et al., 2022; 2024; Taniai et al.; Ito et al., 2025) have emerged as the leading paradigm, systematically overcoming prior limitations by embedding symmetry constraints such as periodicity-preserving message passing, thereby achieving state-of-the-art performance in Crystal Property Prediction (CPP).

However, crystals are, in principle, infinite three-dimensional atomic systems. Current real-space encoders often fail to capture **long-term atomic interactions** (Tantivasadakarn et al., 2024), which are essential for determining physical properties. In particular, these methods typically struggle to represent them, as real-space embeddings with finite receptive fields in multi-edge graph constructions limit their ability to account for long-term effects. As a result, they map distinct crystal structures into the same representation. Figure 2 illustrates these examples. In DFT, these interactions are addressed through boundary conditions and supercell configurations (Makkar & Ghosh, 2021).

A promising alternative is diffraction-space encoding: since every atom contributes to diffraction along specific lattice planes, ideal representation is **guaranteed** to embed complete real-space information without loss (Bouwkamp, 2016), enabling more faithful modeling of long-term correlations. Figure 1 illustrates the relationship between the crystal graph and its diffraction. Diffraction arises from the periodic arrangement of atoms and their interactions with the probing beam, described by form factors. Traditional methods, such as X-ray diffraction, rely on fixed, tabulated atomic form factors that depend only on the scattering vector and atomic species, deriving from historically collected, averaged quantum mechanical calculations and experimental measurements. This makes them incapable of distinguishing between atoms of the same element situated in different local chemical environments, as they ignore crucial structural variations that affect material properties.

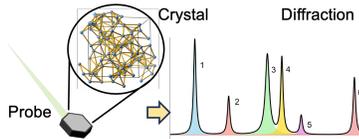


Figure 1: Relationship between crystal and reciprocal space.

In this work, we leverage long-term atomic interactions by incorporating reciprocal-space (diffraction-based) information into crystal representations. Reciprocal space provides a compact, non-approximate description of crystal structures, naturally capturing long-term periodic interactions. To exploit this, we introduce a novel pseudo-particle representation, named PRDNet, that serves as a unique probe, learned through neural networks, and shown to be more effective for differentiating atoms and structural environments than conventional physical probes such as X-rays, electrons, or neutrons. Building on this idea, we develop a multimodal framework that integrates both the graph and diffraction information into the learning process. In addition, we show that the proposed model fulfills the geometric constraints, invariant to rotations, reflections, and translations of crystals. Quantitative evaluations on large-scale datasets, including Materials Project, JARVIS-DFT, and MatBench, demonstrate that our method consistently surpasses state-of-the-art models in common crystal property prediction tasks. In summary, our main contributions are as follows :

- We highlight the fundamental challenge of crystal representation, indicating that existing methods map distinct crystal structures to the same representation. To address this, we introduce diffraction-based representations, which is physically guaranteed to be unique.
- We propose PRDNet, a novel architecture that integrates graph embeddings with a learned pseudo-particle diffraction module. It generates synthetic diffraction patterns that are invariant to crystallographic symmetries.
- We extensively evaluate PRDNet on multiple large-scale benchmarks, including Materials Project, JARVIS-DFT, and MatBench. Our model achieves state-of-the-art performance across a wide range of crystal property prediction tasks, demonstrating its effectiveness.

2 RELATED WORK

Current crystal representations can be broadly categorized into three types: (1) multi-edge graph models; (2) atomic angular embedding; (3) periodic vector-based reference system. Despite their differences, their common limitation is mapping distinct crystal structures onto the same representations, as shown in Figure 2. Specifically, multi-edge crystal graphs, as in CGCNN (Xie &

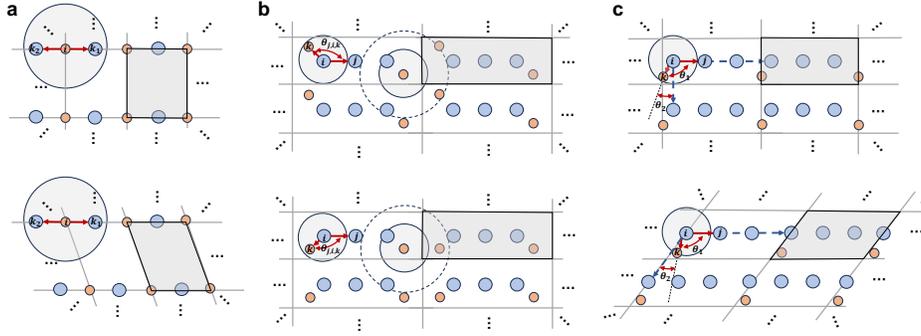


Figure 2: Representation limitations of projecting different atomic periodicity into the same graph representation using (a) multi-edge graphs, (b) atomic angular embedding, and (c) a periodic vector-based reference system. The gray region represents a lattice cell of the 2D crystal.

Grossman, 2018), SchNet (Schütt et al., 2017), MEGNet (Chen et al., 2019), and GATGNN (Louis et al., 2020), define atomic connectivity through cutoff radii, continuous filters, or message-passing and attention mechanisms. They are unable to distinguish distinct crystal systems, since angular information is not considered (Figure 2 a). To address this, models such as ALIGNN (Choudhary & DeCost, 2021) and M3GNet (Chen & Ong, 2022) incorporate bond-angle features, although restricted cutoffs may still yield identical angular relationships (Figure 2 b). Finally, multiple methods extend beyond lattice vectors by introducing periodic vectors, as in MatFormer (Yan et al., 2022) and iConformer/eConformer (Yan et al., 2024), or by employing Transformer-based frameworks, such as Crystalformer (Taniai et al.) and Crystalframer (Ito et al., 2025), to capture broader correlations. However, these models remain limited by their local encodings, which often fail to differentiate structures or capture long-term interactions (Figure 2 c).

Recently, ReGNet (Nie et al., 2025) also introduced a reciprocal-space block to model long-range correlations. Nevertheless, it may produce inconsistent representations by violating the structure dependence of form factors, the details are discussed in Appendix A.2.

3 PRELIMINARIES

Crystal Structures Crystal structures can be described using a fundamental unit, such as a primitive cell, conventional unit cell, Bravais lattice, or asymmetric unit—together with its associated atoms. The unit is defined by a 3×3 lattice matrix that specifies its geometry in real space. Formally, a crystal structure is represented as $\mathcal{M} = (\mathbf{A}, \mathbf{P}, \mathbf{L})$, where \mathbf{A} denotes atomic types, $\mathbf{P} = [\mathbf{p}_1, \dots, \mathbf{p}_N] \in \mathbb{R}^{3 \times N}$ contains the fractional or Cartesian coordinates of the N atoms, and $\mathbf{L} = [\ell_1, \ell_2, \ell_3] \in \mathbb{R}^{3 \times 3}$ defines the periodic lattice in real space. A crystal is an infinite periodic structure, expressed as

$$\hat{\mathbf{P}} = \{\hat{\mathbf{p}}_i \mid \hat{\mathbf{p}}_i = \mathbf{p}_i + k_1 \ell_1 + k_2 \ell_2 + k_3 \ell_3, k_1, k_2, k_3 \in \mathbb{Z}, 1 \leq i \leq N\}, \quad (1)$$

where $\hat{\mathbf{P}}$ denotes the complete set of atomic positions generated by lattice translations. A crystal structure can also be represented as a graph $\mathcal{G} = (\mathcal{V}, \mathcal{E})$, where vertices $\mathcal{V} = \{v_1, v_2, \dots, v_N\}$ encode the atomic attributes, and edges $\mathcal{E} \subseteq \mathcal{V} \times \mathcal{V}$ represent atomic interactions defined by interatomic distances derived from \mathbf{P} and \mathbf{L} , $\hat{\mathbf{v}} = \{\hat{\mathbf{v}}_i \mid \hat{\mathbf{v}}_i = \mathbf{G}(\mathbf{v}_i), 1 \leq i \leq N\}$ where $\hat{\mathbf{v}}$ contains the shared atomic features of atoms occupying symmetry-equivalent sites under the point group operation \mathbf{G} .

Diffraction Diffraction refers to the interaction of probe particles with periodic structures (Cao et al.; Guo et al., 2025). In crystals, diffraction maps the real-space atomic arrangement into momentum (reciprocal) space, where each diffraction feature encodes structural information along specific periodic directions. Since diffraction is uniquely determined by the electron distribution for a given probe, and the electron distribution itself is governed by the potential field arising from the infinite atomic arrangement, diffraction provides a **unique representation** of the real-space crystal structure (Kohn et al., 1996). This process is governed by the *structure factor* (Greenfield et al., 1971), which

describes how atoms scatter incident radiation (e.g., X-rays in XRD). Formally, diffraction is the Fourier transform of the electron density $\rho(\mathbf{r})$ in real space, giving

$$F(\mathbf{Q}) = \int_{\text{unit cell}} \rho(\mathbf{r}) e^{-i\mathbf{Q}\cdot\mathbf{r}} d\mathbf{r}, \quad (2)$$

where \mathbf{r} is the Cartesian position vector and \mathbf{Q} the basis on reciprocal-space. The electron density $\rho(\mathbf{r})$ reflects the spatial distribution of electrons and governs the dispersion properties of the crystal.

For a crystal of discrete atoms at positions \mathbf{r}_j with atomic form factors f_j , the structure factor reduces to (Hubbell et al., 1975)

$$F(\mathbf{Q}) = \sum_{j=1}^N f_j(\mathbf{Q}) e^{-i\mathbf{Q}\cdot\mathbf{r}_j}, \quad (3)$$

where N is the number of atoms in the unit cell. The atomic form factor $f_j(\mathbf{Q})$ specifies the scattering amplitude of atom j and is subject to physical constraints (see Appendix A.2). Thus, each $F(\mathbf{Q})$ encodes the real-space atomic arrangement along a crystallographic direction.

Pseudo-particle Conventional diffraction probes, including X-ray photons, electrons, and neutrons, have intrinsic limitations in reciprocal-space representations (Bouwkamp, 2016). X-rays (Epp, 2016; Cao et al.) and electrons (Glauber & Schomaker, 1953) scatter from the electron cloud, with intensities determined by the atomic form factor f_j , making atoms with similar charge nearly indistinguishable. Neutron diffraction (Shull & Wilkinson, 1953), in contrast, relies on nuclear scattering cross-sections, but heavy atoms of similar mass often show weak contrast. In a numerical framework, these limitations can be addressed by introducing a pseudo-particle with learned particle attributes, acting as a unique probe for reciprocal-space crystal representation, enabling differentiation of atomic arrangements in distinct local environments.

Problem definition Many material properties can be derived from the fundamental equations of electronic behavior, where the dynamics of electrons are fully determined by the external potential imposed by the atomic arrangement in a crystal (Martin, 2020). Crystal property prediction thus aims to estimate a physical property y from the crystal structure, represented as a tuple $(\mathbf{A}, \mathbf{P}, \mathbf{L})$. The target property y may be continuous ($y \in \mathbb{R}$) in regression tasks or categorical ($y \in \{1, 2, \dots, C\}$) in classification tasks with C classes.

4 METHOD

4.1 OVERALL FRAMEWORK

Motivation for Learned Pseudo-Particles Unlike conventional X-ray diffraction, which relies on fixed tabulated form factors, our approach introduces a learned pseudo-particle that incorporates environmental dependence, enabling greater sensitivity to chemical environments and elemental differences. In XRD, the interaction between X-ray photons and atoms (i.e., the form factor) is obtained from the International Tables for Crystallography (Prince, 2004). It is a fixed tabulated value that depends on two factors:

$$f_i^{\text{X-ray}} = f_i^{\text{X-ray}}(|\mathbf{Q}|, f_i^{\text{type}}) \quad (4)$$

where $|\mathbf{Q}|$ is the magnitude of the scattering vector \mathbf{Q} (the reciprocal-space basis), and f_i^{type} denotes the atomic species. Thus, real physical particles cannot distinguish between identical atoms located in different local environments for a given scattering vector \mathbf{Q} . Moreover, the intrinsic physical properties of X-ray photons limit their sensitivity to specific atoms.

This limitation motivates us to design a pseudo-particle that is explicitly sensitive to the local atomic environment while retaining strong discriminability across different elements, making it well-suited for CPP task. Unlike real particles, the learned pseudo-particle is not constrained by the physical limitations of X-rays. We define its form factor as:

$$f_i^{\text{Pseudo}} = f_i^{\text{Pseudo}}(|\mathbf{Q}|, G_\theta(\mathcal{G}), f_i^{\text{type}}), \quad (5)$$

where $G_\theta(\mathcal{G})$ encodes the local chemical environment learned by the graph network.

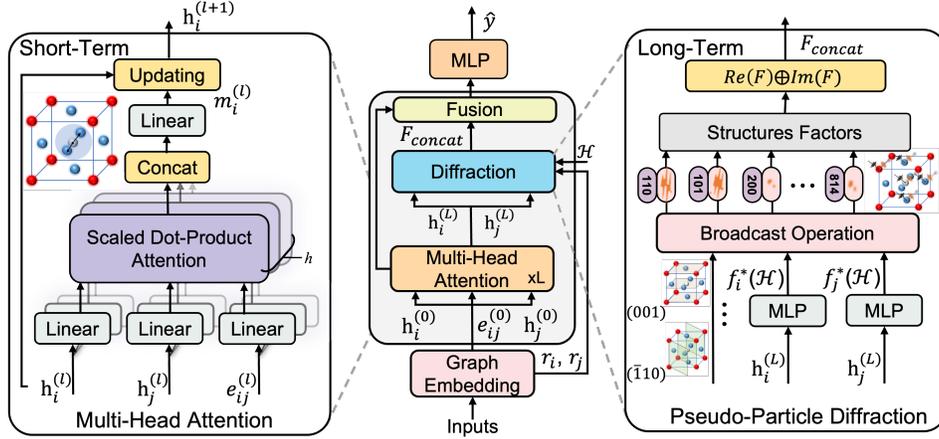


Figure 3: The configuration of PRDNet, which integrates crystal attention and pseudo-particle diffraction to capture both short- and long-term atomic interactions.

Graph embedding A crystal structure is represented as a graph $\mathcal{G} = (\mathcal{V}, \mathcal{E})$, where vertices $\mathcal{V} = \{v_1, v_2, \dots, v_N\}$ correspond to atoms one-hot encoded attributes (Xie & Grossman, 2018) and edges $\mathcal{E} \subseteq \mathcal{V} \times \mathcal{V}$ encode atomic interactions within a cutoff radius. Each atom i is characterized by a node feature $\mathbf{h}_i^{(0)} = \text{Embed}(v_i) \in \mathbb{R}^d$ and coordinates $\mathbf{r}_i = (x_i, y_i, z_i) \in \mathbb{R}^3$. Edge features between atoms i and j are defined as:

$$\mathbf{e}_{ij} = \text{RBF}(d_{ij}) \oplus \text{SBF}(\theta_{ijk}) \oplus d_{ij}, \quad d_{ij} = \|\mathbf{r}_i - \mathbf{r}_j\|, \quad (6)$$

where $\text{RBF}(\cdot)$ denotes a radial basis function, $\text{SBF}(\cdot)$ a spherical basis function (Gasteiger et al.), θ_{ijk} is the angle between bond ij and bond ik , and \oplus indicates concatenation.

Multi-Modal Feature Fusion The integration of graph-based crystal real-space features $\mathbf{h}_i^{(L)}$ and physics-based diffraction representations $\mathbf{F}_{\text{concat}}$ is achieved through a fusion mechanism:

$$\mathbf{g} = \text{GlobalPool}(\{\mathbf{h}_i^{(L)}\}_{i=1}^N), \quad \mathbf{d} = \text{MLP}_{\text{diff}}(\mathbf{F}_{\text{concat}}), \quad \mathbf{z}_{\text{fused}} = \text{MLP}_{\text{fusion}}([\mathbf{g} \oplus \mathbf{d}]). \quad (7)$$

$\text{GlobalPool}(\cdot)$ aggregates node features across the entire crystal structure, $\text{MLP}_{\text{diff}}(\cdot)$ maps physics-based descriptors to the embedding space, and $\text{MLP}_{\text{fusion}}(\cdot)$ produces the final fused representation.

Model Invariance Crystals are inherently symmetrical. Following existing work (Yan et al., 2024), we force the model prediction to be invariant to $E(3)$ group (i.e., the rotation, reflection, and translation of input crystals). Specifically, according to Eq. 7, the final representation output $\mathbf{z}_{\text{fused}}$ depends on the \mathbf{g} and \mathbf{d} . Since \mathbf{g} depends on the relative geometric features d_{ij} and θ_{ijk} (Eq.6) that remain unchanged under $E(3)$ operations, \mathbf{g} is $E(3)$ -invariant. Consequently, because \mathbf{d} is also $E(3)$ -invariant, the model output is $E(3)$ -invariant, as shown in Section 4.3.

4.2 STRUCTURE MODELING

Multi-Head Attention Projections The PRDNet message-passing layer augments conventional graph attention mechanisms by integrating edge features and physics-informed constraints. Using a multi-head attention framework, it captures information from local atomic environments. Given node features $\mathbf{h}_i^{(l)}, \mathbf{h}_j^{(l)} \in \mathbb{R}^d$ and edge feature \mathbf{e}_{ij} at layer l , we first compute the query, key, value, and edge projections for each attention head $h \in \{1, 2, \dots, H\}$:

$$\mathbf{Q}^{(h)} = \mathbf{W}_Q^{(h)} \mathbf{h}^{(l)}, \quad \mathbf{K}^{(h)} = \mathbf{W}_K^{(h)} \mathbf{h}^{(l)}, \quad \mathbf{V}^{(h)} = \mathbf{W}_V^{(h)} \mathbf{h}^{(l)}, \quad \mathbf{E}_{ij}^{(h)} = \mathbf{W}_E^{(h)} \mathbf{e}_{ij}, \quad (8)$$

where $\mathbf{W}_Q^{(h)}, \mathbf{W}_K^{(h)}, \mathbf{W}_V^{(h)} \in \mathbb{R}^{d_h \times d}$ and $\mathbf{W}_E^{(h)} \in \mathbb{R}^{d_h \times d_e}$ are learnable projection matrices. Then the attention scores are computed as:

$$\mathbf{q}_{ij}^{(h)} = \mathbf{Q}_i^{(h)} \oplus \mathbf{Q}_i^{(h)} \oplus \mathbf{Q}_i^{(h)}, \mathbf{k}_{ij}^{(h)} = \mathbf{K}_i^{(h)} \oplus \mathbf{K}_j^{(h)} \oplus \mathbf{E}_{ij}^{(h)}, \alpha_{ij}^{(h)} = \frac{\mathbf{q}_{ij}^{(h)} \odot \mathbf{k}_{ij}^{(h)}}{\sqrt{3d_h}}, \quad (9)$$

where \oplus denotes concatenation and \odot represents element-wise multiplication.

Gated Message and Aggregation The message aggregation incorporates both value information and attention-modulated gating. For each attention head h , the value vector and gating factor are defined as:

$$\mathbf{v}_{ij}^{(h)} = \mathbf{V}_i^{(h)} \oplus \mathbf{V}_j^{(h)} \oplus \mathbf{E}_{ij}^{(h)}, \mathbf{g}_{ij}^{(h)} = \sigma\left(\text{LayerNorm}(\alpha_{ij}^{(h)})\right), \mathbf{m}_{ij}^{(h)} = \mathbf{W}_{\text{msg}} \mathbf{v}_{ij}^{(h)} \odot \mathbf{g}_{ij}^{(h)}, \quad (10)$$

where $\sigma(\cdot)$ is the sigmoid activation, \odot denotes elementwise multiplication, and $\mathbf{W}_{\text{msg}} \in \mathbb{R}^{3d_h \times 3d_h}$ is a learnable transformation matrix. The gating term $\mathbf{g}_{ij}^{(h)}$ acts as an adaptive filter, modulating the contribution of each message according to the attention scores. Messages from all neighbors and attention heads are then aggregated and projected back to the hidden dimension:

$$\mathbf{m}_i^{\text{agg}} = \bigoplus_{j \in \mathcal{N}(i)} \bigoplus_{h=1}^H \mathbf{m}_{ij}^{(h)}, \mathbf{h}_i^{(l+1)} = \beta_i \odot \mathbf{h}_i^{(l)} + (1 - \beta_i) \odot \text{SiLU}\left(\text{BatchNorm}(\mathbf{W}_{\text{concat}} \mathbf{m}_i^{\text{agg}})\right), \quad (11)$$

where $\mathcal{N}(i)$ denotes the neighbors of node i , \bigoplus indicates concatenation, H is the number of attention heads, and $\mathbf{W}_{\text{concat}}$ projects the concatenated features into the hidden dimension.

4.3 PSEUDO-PARTICLE RAY DIFFRACTION MODELING

The pseudo-particle ray diffraction module incorporates particle diffraction theory into the neural network architecture. This module computes structure factors from the learned atomic representations and fuses this physical information with graph-based features.

Learnable Atomic Form Factors Unlike traditional crystallographic calculations that rely on tabulated atomic form factors, the pseudo-particle form factor $f_i(\mathbf{Q})$ is defined as

$$f_i^*(\mathbf{Q}) = f_i(|\mathbf{Q}|, G_\theta(\mathcal{G}), f_i^{\text{type}}), \quad (12)$$

where $|\mathbf{Q}|$ depends on the magnitude of the scattering vector \mathbf{Q} , $G_\theta(\mathcal{G})$ captures modifications due to the local chemical environment, and f_i^{type} encodes species-specific attributes. In PRDNet, these adaptive form factors are not fixed but learned through a dedicated form-factor layer that maps node embeddings to scattering strengths:

$$f_i^*(\mathcal{H}) = \text{MLP}_{\text{form}}(\mathbf{h}_i^{(L)}) \in \mathbb{R}^{N_{\text{hkl}}}, \quad (13)$$

where $\text{MLP}_{\text{form}} : \mathbb{R}^d \rightarrow \mathbb{R}^{N_{\text{hkl}}}$, and $\mathbf{h}_i^{(L)}$ denotes the final node representation. Let f_i^* denotes the dimension corresponding to a specific $(h, k, l) \in \mathcal{H}$, with (h, k, l) and \mathcal{H} introduced below.

Miller Index Selection and Structure Factors To ensure comprehensive coverage of reciprocal space, we employ a systematic selection of Miller indices. Each (h, k, l) triplet specifies a crystallographic direction, corresponding to a unique scattering vector \mathbf{Q} .

$$\mathcal{H}_0 = \{(h, k, l) \in \mathbb{Z}^3 : |h|, |k|, |l| \leq C_{\text{max}}, \text{gcd}(|h|, |k|, |l|) = 1\} \quad (14)$$

$\text{gcd}(\cdot)$ denotes the greatest common divisor (GCD). The constraint $\text{gcd}(|h|, |k|, |l|) = 1$ ensures that all fundamental reflections are considered, avoiding redundant higher-order reflections. The parameter $C_{\text{max}} = 8$ controls the resolution in reciprocal space. To guarantee that the index set is closed under symmetry, we define

$$\mathcal{H} = \{\pm \text{perm}(h, k, l) : (h, k, l) \in \mathcal{H}_0\}, \quad (15)$$

where $\text{perm}(h, k, l)$ denotes all permutations of (h, k, l) and the prefactor \pm accounts for inversion. By construction, \mathcal{H} is closed under all crystallographic operations.

The complete diffraction signature is constructed by computing structure factors for all selected Miller indices $\mathbf{F}(\mathcal{H}) = [F_{hkl}]_{(h,k,l) \in \mathcal{H}}$. The structure factors of pseudo-particle ray diffraction, denoted as $\mathbf{F}(\mathcal{H})$, are converted to real values by applying the real part operator. The real and imaginary components are obtained by summing over atoms with the corresponding form factor weights:

$$\text{Re}(F_{hkl}) = \sum_{i=1}^N f_i^* \cos(2\pi \mathbf{h} \cdot \mathbf{r}_i^T), \quad \text{Im}(F_{hkl}) = \sum_{i=1}^N f_i^* \sin(2\pi \mathbf{h} \cdot \mathbf{r}_i^T) \quad (16)$$

where f_i^* is the learned atomic form factor for atom i , $\mathbf{h} = (h, k, l)^T$ is the reciprocal lattice vector, and $\mathbf{r}_i = (x_i, y_i, z_i)$ represents the fractional coordinates of atom i . The real and imaginary parts are then flattened to construct the diffraction feature tensor:

$$\mathbf{F}_{\text{concat}} = \text{flatten}(\text{Re}(\mathbf{F}(\mathcal{H})) \oplus \text{Im}(\mathbf{F}(\mathcal{H}))) \in \mathbb{R}^{2N_{\text{hkl}}} \quad (17)$$

The forward propagation process is presented in Algorithm 1, and a case study on the crystal CaF_2 is provided in Appendix C.

Invariance in pseudo-particle diffraction Let G be the crystallographic operations acting on fractional coordinates by $g : \mathbf{r} \mapsto g \cdot \mathbf{r} = R_g \mathbf{r} + \mathbf{t}_g, g \in G$, where R_g (i.e., rotations and reflections) is an integer unimodular matrix ($\det R_g = \pm 1$) that maps Miller indices to integer triplets. And \mathbf{t}_g the translational part. Denote a Miller index by $\mathbf{h} = (h, k, l)^T \in \mathbb{Z}^3$ and the set of indices by \mathcal{H} . The set \mathcal{H} is closed under the action of G , i.e.,

$$\forall g \in G, \forall \mathbf{h} \in \mathcal{H} \quad \Rightarrow \quad g \cdot \mathbf{h} = R_g \mathbf{h} + \mathbf{t}_g = R_g \mathbf{h} \in \mathcal{H}. \quad (18)$$

Under g the coordinates become $g \cdot \mathbf{r}_i = R_g \mathbf{r}_i + \mathbf{t}_g$ and the Miller index maps to $g \cdot \mathbf{h} = R_g \mathbf{h}$. Hence

$$\begin{aligned} F_{g \cdot \mathbf{h}}(\{g \cdot \mathbf{r}_i\}) &= \sum_{i=1}^N f_i^* \exp\left(2\pi i (R_g \mathbf{h}) \cdot (R_g \mathbf{r}_i + \mathbf{t}_g)\right) \\ &= \exp\left(2\pi i (R_g \mathbf{h}) \cdot \mathbf{t}_g\right) \sum_{i=1}^N f_i^* e^{2\pi i \mathbf{h} \cdot \mathbf{r}_i} = e^{2\pi i \phi(g, \mathbf{h})} F_{\mathbf{h}}(\{\mathbf{r}_i\}) \end{aligned} \quad (19)$$

The phase $\phi(g, \mathbf{h}) = (R_g \mathbf{h}) \cdot \mathbf{t}_g$ arises from the translation. Because it is always an integer, the factor $e^{2\pi i \phi(g, \mathbf{h})} = 1$, which ensures that the representation remains invariant under crystallographic operations.

5 EXPERIMENTS

Datasets We benchmark the models using three evaluation suites. The definitions and background of the regression and classification targets are introduced in the Appendix E.

- **Materials Project (MP) Database:** We use stable structures retrieved from the Materials Project (Jain et al., 2020), comprising 122,959 entries with annotated formation energy, band gap, and metal/non-metal classification labels. Additionally, 9,473 of these entries include mechanical properties such as bulk modulus, shear modulus and Young’s modulus. The dataset is managed using the *Atomic Simulation Environment (ASE)*, which provides a unified dataloader for streamlined access (Cao & Zhang, 2025b).

Table 1: Mean Absolute Error and Accuracy comparison on the MP.

Method	Form. Energy eV/atom	Bandgap eV	Bulk Modulus log(GPa)	Shear Modulus log(GPa)	Young’s Modulus log(GPa)	Metal/Non-metal Acc(%)
CGCNN (Xie & Grossman, 2018)	0.041	0.262	0.079	0.162	0.155	87.5
SchNet (Schütt et al., 2017)	0.038	0.344	0.092	0.129	0.143	82.8
MEGNET (Chen et al., 2019)	0.053	0.307	0.134	0.206	0.189	86.6
GATGNN (Louis et al., 2020)	0.083	0.343	0.051	<u>0.111</u>	0.109	86.3
Matformer (Yan et al., 2022)	0.035	0.193	0.089	0.306	0.291	<u>92.7</u>
Crystalformer (Taniai et al.)	0.049	0.251	0.064	0.140	0.127	86.5
Crystalformer (Ito et al., 2025)	<u>0.030</u>	0.216	<u>0.047</u>	0.118	<u>0.106</u>	87.5
eComFormer (Yan et al., 2024)	0.033	<u>0.153</u>	0.088	0.269	0.311	82.5
PRDNet	0.028	0.151	0.035	0.108	0.104	93.3

Table 2: Mean Absolute Error comparison on the JARVIS-DFT (left) and MB (right).

Method	JARVIS-DFT				MB			
	Form. Energy eV/atom	Bandgap eV	Bulk Modulus log(GPa)	Shear Modulus log(GPa)	jdft2d eV/atom	mp_e_form eV/atom	log_gvrh log(GPa)	dielectric unitless
CGCNN	0.038	<u>0.144</u>	0.125	0.163	0.050	0.027	<u>0.066</u>	0.541
SchNet	0.074	<u>0.278</u>	0.143	0.225	0.056	0.042	0.085	0.341
MEGNET	0.074	0.221	0.124	0.214	0.052	0.036	0.098	0.459
GATGNN	0.069	0.235	0.078	0.160	0.046	0.032	0.087	0.408
Matformer	<u>0.033</u>	0.207	0.101	0.157	0.072	0.023	0.071	0.764
Crystalformer	0.052	0.248	0.075	0.146	0.071	<u>0.020</u>	0.080	<u>0.244</u>
Crystalformer	0.048	0.208	<u>0.065</u>	<u>0.144</u>	0.056	0.065	0.084	0.248
eComFormer	0.119	0.260	0.118	0.243	0.031	<u>0.020</u>	0.085	0.543
PRDNet	0.032	0.140	0.064	0.122	<u>0.038</u>	0.019	0.058	0.242

- **JARVIS-DFT (dft_3d)**: This dataset contains 75,993 entries, each annotated with formation energy, band gap, bulk modulus, and shear modulus (Choudhary et al., 2020).
- **Matbench (MB) Suite**: We evaluate the models on several tasks from the Matbench suite (Dunn et al., 2020): matbench_jdft2d (636 entries; exfoliation energy), matbench_mp_e_form (132,752 entries; formation energy), matbench_log_gvrh (10,987 entries; shear modulus), and matbench_dielectric (4,764 entries; refractive index).

Implementation details The specific hyperparameters used are listed in Appendix D. All models follow the original open-source settings without additional tuning. Model performance is evaluated using the Mean Absolute Error (MAE) and accuracy. All implementations are based on the PyTorch framework (Paszke et al., 2019) and trained on NVIDIA GeForce RTX 3090 GPUs.

5.1 RESULTS

Benchmarks Performance Across the MP, JARVIS-DFT, and Matbench benchmarks, PRDNet consistently delivers superior or competitive performance compared with existing models. On the MP dataset (Table 1), PRDNet surpasses all baselines, achieving the lowest errors in formation energy (0.028 eV/atom), band gap (0.151 eV), bulk modulus (0.035 log(GPa)), shear modulus (0.108 log(GPa)), and Young’s modulus (0.104 log(GPa)), while also reaching the highest metal/non-metal classification accuracy (93.3%). On JARVIS-DFT (Table 2), PRDNet again outperforms all baselines, attaining the best results across all tasks, including formation energy (0.032 eV/atom), band gap (0.140 eV), bulk modulus (0.064 log(GPa)), and shear modulus (0.122 log(GPa)). On the Matbench benchmark (Table 2), PRDNet achieves the lowest errors in formation energy (0.019 eV/atom), shear modulus (0.058 log(GPa)) and refractive index (0.242 (unitless)), while maintaining competitive performance in exfoliation energy prediction. These results show that PRDNet generalizes effectively across diverse datasets and provides balanced improvements in both energy-related and mechanical property predictions, underscoring its robustness and versatility for crystal property modeling.

Ablation Study To validate the effectiveness of each component in the PRDNet architecture, we perform systematic ablation studies that isolate the contributions of individual modules and design

Table 3: Ablation study on the Materials Project. **Diff.** indicates whether the diffraction module is used, **MH** denotes single-head or multi-head attention, **Res.** specifies whether residual connections are applied during node attribute updates, and **EF** refers to the inclusion of edge features (see Appendix B).

Model	Diff.	MH	Res.	EF	Form. Energy	Bandgap	Bulk Modulus	Shear Modulus	Young’s Modulus	Metal/Non-metal
					MAE(eV/atom)	MAE(eV)	MAE(log(GPa))	MAE(log(GPa))	MAE(log(GPa))	Acc(%)
Default	✓	✓	✓	✓	0.028	0.151	0.035	0.108	0.104	93.3
NoDiff	×	✓	✓	✓	0.041	0.361	0.081	0.171	0.162	81.9
SingleHead	✓	×	✓	✓	0.040	0.318	0.067	0.166	0.181	89.3
NoRes	✓	✓	×	✓	0.038	0.297	0.077	0.204	0.222	82.7
NoEdge	✓	✓	✓	×	0.043	0.355	0.071	0.198	0.179	80.1

Table 4: Pseudo-Particle v.s. X-ray Photon

Method	MP		JARVIS-DFT		MB	
	Pseudo-Particle	X-ray	Pseudo-Particle	X-ray	Pseudo-Particle	X-ray
Form. Energy (MAE eV/atom)	0.028	0.085	0.032	0.103	0.019	0.063
Bandgap (MAE eV)	0.151	0.271	0.140	0.331	-	-
Bulk Modulus (MAE log(GPa))	0.035	0.094	0.064	0.101	-	-
Shear Modulus (MAE log(GPa))	0.108	0.322	0.122	0.256	0.058	0.111
Young’s Modulus (MAE log(GPa))	0.104	0.291	-	-	-	-
Exfo. Energy (MAE eV/atom)	-	-	-	-	0.038	0.089
Refractive Index (MAE unitless)	-	-	-	-	0.242	0.476
Metal/Non-metal (Acc %)	93.3	78.9	-	-	-	-

choices. We evaluate PRDNet across diverse property prediction tasks using the Materials Project, JARVIS-DFT and Matbench databases, ensuring a comprehensive assessment. Table 3 presents the ablation results on the MP dataset, while Appendix B, Table 5, and Table 6 report the results on JARVIS-DFT and Matbench, respectively. The results show that each component is essential for optimal performance. Removing the diffraction module causes the obversely performance drop, underscoring its critical role. Likewise, using single-head attention, removing residual connections, or excluding edge features consistently degrades performance, indicating that multi-head attention, residual updates, and edge features collectively strengthen representation learning. These findings confirm the effectiveness of our default architecture, in which all modules work synergistically to achieve the highest accuracy across material property predictions.

Pseudo-Particle vs. X-ray Photon For evidencing the enriched representation of Pseudo-Particle on crystal sensitivity, we compare two PRDNet variants: (1) PRDNet-Learned: employs learned pseudo-particle form factors f_i^* (Eq. 13); (2) PRDNet-Tabulated: substitutes f_i^* with tabulated X-ray photon form factors. As summarized in Table 4, the pseudo-particle representation consistently outperforms the X-ray counterpart across all datasets and property prediction tasks. Specifically, it achieves lower MAEs for formation energy, bandgap, and mechanical moduli, while also delivering higher classification accuracy in metal/non-metal discrimination.

Number of Miller Indices Each Miller index specifies a crystallographic direction. The choice of a sufficiently large set of Miller indices, \mathcal{H}_0 , is crucial for adequately representing reciprocal space. We evaluate the performance of PRDNet using 100, 200, 300, 500, and 1000 Miller indices on the MP dataset for both formation energy and band gap prediction tasks. As shown in Figure 4, using 300 indices provides a good balance between computational cost and predictive accuracy.

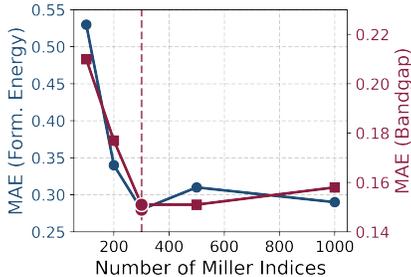


Figure 4: Performance of PRDNet on formation energy and band gap prediction across different numbers of Miller indices.

6 CONCLUSION

In this work, we introduce a Pseudo-Particle Ray Diffraction Neural Network (PRDNet) for crystal structure property prediction. PRDNet outperforms previous approaches by capturing long-term atomic correlations through a physically invariant reciprocal-space representation embedded within the neural network. The learned pseudo-particle attributes act as a novel probe, exhibiting higher

sensitivity than any known physical particle to atomic type, local chemical environment, and diffraction directions. Experiments demonstrate that PRDNet provides a principled framework for integrating crystallographic theory with deep learning, offering a novel conception of invariant crystal representation and achieving SOTA performance across multiple properties and databases.

Limitations The benefits of PRDNet’s diffraction-based reciprocal-space representation do not directly transfer to non-periodic structures. Moreover, the current representation is difficult to invert for reconstructing structures from reciprocal-space sampling, limiting its applicability to direct crystal structure prediction tasks.

Future Work Building on this work, future research may explore:

- **Extended Physics Integration:** Incorporating additional physical phenomena, such as phonon interactions, electronic structures, and magnetic properties.
- **Multi-Scale Modeling:** Expanding PRDNet to handle multiple length scales simultaneously, from atomic to mesoscopic structures.
- **Structure Identification:** Integrating with experimental design frameworks for crystal structure identification (XQueryer, Cao et al.), structure refinement (WPEM, Cao & Zhang (2024; 2025a)), and property inference (PRDNet) to accelerate materials discovery.

REFERENCES

- Feliks Aleksandrovich Berezin and Mikhail Shubin. *The Schrödinger Equation*, volume 66. Springer Science & Business Media, 2012.
- Christoffel Jacob Bouwkamp. Diffraction theory. 2016.
- Bin Cao and Tong-Yi Zhang. Pyxplore (revision 56c956f), 2025a. URL <https://huggingface.co/datasets/caobin/PyXplore>.
- Bin Cao and Tong-Yi Zhang. Cppbenchmark (revision 261622f), 2025b. URL <https://huggingface.co/datasets/caobin/Cppbenchmark>.
- Bin Cao and Tongyi Zhang. WPEM manual. 12 2024. doi: 10.6084/m9.figshare.28078985.v3. URL https://figshare.com/articles/dataset/WPEM_manual/28078985.
- Bin Cao, Yang Liu, Zinan Zheng, Ruifeng Tan, Jia Li, and Tong-yi Zhang. Simxrd-4m: Big simulated x-ray diffraction data and crystal symmetry classification benchmark. In *The Thirteenth International Conference on Learning Representations*.
- Chi Chen and Shyue Ping Ong. A universal graph deep learning interatomic potential for the periodic table. *Nature Computational Science*, 2(11):718–728, 2022.
- Chi Chen, Weike Ye, Yunxing Zuo, Chen Zheng, and Shyue Ping Ong. Graph networks as a universal machine learning framework for molecules and crystals. *Chemistry of Materials*, 31(9):3564–3572, 2019.
- Kamal Choudhary and Brian DeCost. Atomistic line graph neural network for improved materials property predictions. *npj Computational Materials*, 7(1):185, 2021.
- Kamal Choudhary, Kevin F Garrity, Andrew CE Reid, Brian DeCost, Adam J Biacchi, Angela R Hight Walker, Zachary Trautt, Jason Hattrick-Simpers, A Gilad Kusne, Andrea Centrone, et al. The joint automated repository for various integrated simulations (jarvis) for data-driven materials design. *npj computational materials*, 6(1):173, 2020.
- Alexander Dunn, Qi Wang, Alex Ganose, Daniel Dopp, and Anubhav Jain. Benchmarking materials property prediction methods: the matbench test set and automatminer reference algorithm. *npj Computational Materials*, 6(1):138, 2020.
- J Epp. X-ray diffraction (xrd) techniques for materials characterization. In *Materials characterization using nondestructive evaluation (NDE) methods*, pp. 81–124. Elsevier, 2016.

- Helmer Fjellvåg. Symmetry-operations, point groups, space groups and crystal structure. *Department of Chemistry, University of Oslo*, 1994.
- Johannes Gasteiger, Janek Groß, and Stephan Günnemann. Directional message passing for molecular graphs. In *International Conference on Learning Representations*.
- MJ Gillan. Calculation of the vacancy formation energy in aluminium. *Journal of Physics: Condensed Matter*, 1(4):689, 1989.
- Roy Glauber and Verner Schomaker. The theory of electron diffraction. *Physical Review*, 89(4):667, 1953.
- AJ Greenfield, J Wellendorf, and Nathan Wiser. X-ray determination of the static structure factor of liquid na and k. *Physical Review A*, 4(4):1607, 1971.
- Gabe Guo, Tristan Luca Saidi, Maxwell W Terban, Michele Valsecchi, Simon JL Billinge, and Hod Lipson. Ab initio structure solutions from nanocrystalline powder diffraction data via diffusion models. *Nature Materials*, pp. 1–9, 2025.
- John Howard Hubbell, Wm J Veigele, EA Briggs, RT Brown, DT Cromer, and d RJ Howerton. Atomic form factors, incoherent scattering functions, and photon scattering cross sections. *Journal of physical and chemical reference data*, 4(3):471–538, 1975.
- Olexandr Isayev, Corey Oses, Cormac Toher, Eric Gossett, Stefano Curtarolo, and Alexander Tropsha. Universal fragment descriptors for predicting properties of inorganic crystals. *Nature communications*, 8(1):15679, 2017.
- Yusei Ito, Tatsunori Taniai, Ryo Igarashi, Yoshitaka Ushiku, and Kanta Ono. Rethinking the role of frames for se (3)-invariant crystal structure modeling. In *The Thirteenth International Conference on Learning Representations*, 2025.
- Anubhav Jain, Joseph Montoya, Shyam Dwaraknath, Nils ER Zimmermann, John Dagdelen, Matthew Horton, Patrick Huck, Donny Winston, Shreyas Cholia, Shyue Ping Ong, et al. The materials project: Accelerating materials design through theory-driven data and tools. *Handbook of Materials Modeling: Methods: Theory and Modeling*, pp. 1751–1784, 2020.
- Jong Hyun Jung, Cheol-Hwan Park, and Jisoon Ihm. A rigorous method of calculating exfoliation energies from first principles. *Nano letters*, 18(5):2759–2765, 2018.
- Anubha Kalra, Andrew Lowe, and A Al Jumaily. An overview of factors affecting the skins youngs modulus. *J. Aging Sci*, 4(2):1000156, 2016.
- Walter Kohn, Axel D Becke, and Robert G Parr. Density functional theory of electronic structure. *The journal of physical chemistry*, 100(31):12974–12980, 1996.
- Zhixun Li, Bin Cao, Rui Jiao, Liang Wang, Ding Wang, Yang Liu, Dingshuo Chen, Jia Li, Qiang Liu, Yu Rong, et al. Materials generation in the era of artificial intelligence: A comprehensive survey. *arXiv preprint arXiv:2505.16379*, 2025.
- Steph-Yves Louis, Yong Zhao, Alireza Nasiri, Xiran Wang, Yuqi Song, Fei Liu, and Jianjun Hu. Graph convolutional neural networks with global attention for improved materials property prediction. *Physical Chemistry Chemical Physics*, 22(32):18141–18148, 2020.
- Akio Makishima and John D Mackenzie. Calculation of bulk modulus, shear modulus and poisson’s ratio of glass. *Journal of Non-crystalline solids*, 17(2):147–157, 1975.
- Priyanka Makkar and Narendra Nath Ghosh. A review on the use of dft for the prediction of the properties of nanomaterials. *RSC advances*, 11(45):27897–27924, 2021.
- Richard M Martin. *Electronic structure: basic theory and practical methods*. Cambridge university press, 2020.
- Gregory P Meyer. An alternative probabilistic interpretation of the huber loss. In *Proceedings of the ieeecv/cvf conference on computer vision and pattern recognition*, pp. 5261–5269, 2021.

- Jianan Nie, Peiyao Xiao, Kaiyi Ji, and Peng Gao. Regnet: Reciprocal space-aware long-range modeling and multi-property prediction for crystals. *arXiv preprint arXiv:2502.02748*, 2025.
- Adam Paszke, Sam Gross, Francisco Massa, Adam Lerer, James Bradbury, Gregory Chanan, Trevor Killeen, Zeming Lin, Natalia Gimelshein, Luca Antiga, et al. Pytorch: An imperative style, high-performance deep learning library. *Advances in neural information processing systems*, 32, 2019.
- Edward Prince. *International Tables for Crystallography, Volume C: Mathematical, physical and chemical tables*. Springer Science & Business Media, 2004.
- Kristof Schütt, Pieter-Jan Kindermans, Huziel Enoc Saucedo Felix, Stefan Chmiela, Alexandre Tkatchenko, and Klaus-Robert Müller. Schnet: A continuous-filter convolutional neural network for modeling quantum interactions. *Advances in neural information processing systems*, 30, 2017.
- CG Shull and MK Wilkinson. Neutron diffraction studies of various transition elements. *Reviews of Modern Physics*, 25(1):100, 1953.
- Tianhao Su, Bin Cao, Shunbo Hu, Musen Li, and Tong-Yi Zhang. Cgwgan: crystal generative framework based on wyckoff generative adversarial network. *Journal of Materials Informatics*, 4(4):N–A, 2024.
- Tatsunori Taniai, Ryo Igarashi, Yuta Suzuki, Naoya Chiba, Kotaro Saito, Yoshitaka Ushiku, and Kanta Ono. Crystalformer: Infinitely connected attention for periodic structure encoding. In *The Twelfth International Conference on Learning Representations*.
- Nathanan Tantivasadakarn, Ryan Thorngren, Ashvin Vishwanath, and Ruben Verresen. Long-range entanglement from measuring symmetry-protected topological phases. *Physical Review X*, 14(2):021040, 2024.
- Tian Xie and Jeffrey C Grossman. Crystal graph convolutional neural networks for an accurate and interpretable prediction of material properties. *Physical review letters*, 120(14):145301, 2018.
- Keqiang Yan, Yi Liu, Yuchao Lin, and Shuiwang Ji. Periodic graph transformers for crystal material property prediction. *Advances in Neural Information Processing Systems*, 35:15066–15080, 2022.
- Keqiang Yan, Cong Fu, Xiaofeng Qian, Xiaoning Qian, and Shuiwang Ji. Complete and efficient graph transformers for crystal material property prediction. *arXiv preprint arXiv:2403.11857*, 2024.
- J Zaanen, GA Sawatzky, and JW Allen. Band gaps and electronic structure of transition-metal compounds. *Physical review letters*, 55(4):418, 1985.
- Ruiming Zhu, Wei Nong, Shuya Yamazaki, and Kedar Hippalgaonkar. Wycryst: Wyckoff inorganic crystal generator framework. *Matter*, 7(10):3469–3488, 2024.

A ADDITIONAL DETAILS

A.1 CRYSTAL INVARIANCE

The representation of a crystal structure must satisfy several fundamental **invariance properties** to reflect the physical symmetries inherent in periodic materials (Li et al., 2025). These include:

- **Permutation invariance:** Let $f(\mathcal{G})$ denote a representation of a crystal graph $\mathcal{G} = (\mathcal{V}, \mathcal{E})$, where \mathcal{V} is the set of atoms and \mathcal{E} the set of edges. Then, for any permutation π of the node indices, we require

$$f(\mathcal{G}) = f(\pi(\mathcal{G})), \quad (20)$$

meaning that relabeling atoms does not alter the representation. This property is naturally satisfied in graph-based models.

- **Translation invariance:** If all atomic positions \mathbf{r} are shifted by a vector $\mathbf{t} \in \mathbb{R}^3$, i.e., $\mathbf{r} \rightarrow \mathbf{r} + \mathbf{t}$, then

$$f(\{\mathbf{r}\}) = f(\{\mathbf{r} + \mathbf{t}\}), \quad (21)$$

ensuring the representation is invariant under global translations.

- **Rotation invariance:** For any rotation matrix $R \in \text{SO}(3)$, the representation must satisfy

$$f(\{\mathbf{r}_i\}) = f(\{R\mathbf{r}_i\}), \quad (22)$$

i.e., the representation remains unchanged under rigid body rotations.

- **Periodic invariance:** For any lattice translation vector $\mathbf{T} \in \mathbb{Z}^3$, the atomic positions \mathbf{r}_i and $\mathbf{r}_i + \mathbf{T}$ should yield the same representation:

$$f(\{\mathbf{r}_i\}) = f(\{\mathbf{r}_i + \mathbf{T}\}), \quad (23)$$

capturing the periodicity of the crystal lattice.

These four invariance properties are essential for any representation of matter based on a periodic unit cell. Beyond these, **symmetry invariance** plays a crucial role in crystallographic systems.

Symmetry invariance requires that atoms related by a space group symmetry operation, such as those occupying the same Wyckoff position, must be treated equivalently in the representation. If a symmetry operation G maps atomic coordinates \mathbf{r} to $G(\mathbf{r})$, then the representation must satisfy

$$f(\mathbf{r}) = f(G(\mathbf{r})). \quad (24)$$

Such symmetry operations include:

- **Identity** (E): $G(\mathbf{r}) = \mathbf{r}$. This operation is always present by group theory.
- **Inversion** ($\bar{1}$): $G(\mathbf{r}) = -\mathbf{r}$. Crystals exhibiting this symmetry are called *centrosymmetric*.
- **Rotation** (C_n): $G(\mathbf{r}) = R_n\mathbf{r}$, where R_n is a rotation matrix corresponding to a $360^\circ/n$ rotation about a symmetry axis.
- **Mirror reflection** (σ): $G(\mathbf{r}) = \mathbf{r} - 2(\mathbf{r} \cdot \hat{n})\hat{n}$, reflecting the position across a mirror plane with normal vector \hat{n} .

In crystallography, certain symmetry operations combine rotation or reflection with fractional lattice translations, giving rise to **glide planes** and **screw axes** (Fjellvåg, 1994). These compound operations are essential for defining space groups but are not directly relevant to the basis invariance required for representation learning.

A.2 PHYSICAL CONSTRAINTS OF DIFFRACTION

Recent work, such as ReGNet (Nie et al., 2025), incorporates reciprocal-space information to capture long-term atomic interactions. The model introduces a dedicated reciprocal block that approximates the structure factor, functioning in a manner similar to Eq. 3, and achieves improved performance. In ReGNet, reciprocal-space information is approximated through a simplified Fourier-like transformation. However, this approximation omits several critical components and consequently fails to preserve key physical properties inherent to reciprocal-space representations.

- **Dependence:** The atomic form factor $f_j(\mathbf{Q})$, as defined in Eq. 3, is not a constant. It inherently depends on three fundamental factors: the atomic species, the local atomic environment, and the scattering vector \mathbf{Q} . Preserving these dependencies is crucial for maintaining physical fidelity in diffraction-based modeling.
- **Consistency:** According to the Schrodinger equation (Berezin & Shubin, 2012), the charge density (or electron distribution) is uniquely determined by the atomic configuration. Therefore, the reciprocal-space representation must be consistent with this determinism. ReGNet introduces multiple reciprocal blocks that evolve independently, leading to inconsistencies and instability in the reciprocal embedding.

In ReGNet, the reciprocal embedding is computed as:

$$F(\mathbf{Q}) = \sum_j h_j^\ell \cdot e^{-i\mathbf{Q} \cdot \mathbf{r}_j} \quad (25)$$

where h_j^ℓ is a learnable embedding that evolves through network layers. This deviates from the physical structure factor $F(\mathbf{Q})$ by omitting key components:

- **Missing atomic form factor dependence:** The diffraction factor $f_j(\mathbf{Q})$ should be expressed as:

$$f_j(\mathbf{Q}) = f_j(|\mathbf{Q}|, G_\theta(\mathcal{G}), f_j^{\text{type}}) \quad (26)$$

where $|\mathbf{Q}|$ captures the dependence on the magnitude of the scattering vector, $G_\theta(\mathcal{G})$ reflects the local environment, and f_j^{type} encodes atomic species. ReGNet’s embedding h_j^ℓ lacks this explicit structure.

- **Violation of reciprocal-space uniqueness:** The Fourier transform $F(\mathbf{Q})$ of the charge density $\rho(\mathbf{r})$ is uniquely defined by a given atomic configuration. ReGNet’s use of multiple independently parameterized reciprocal blocks violates this uniqueness, potentially leading to non-physical or inconsistent representations.

A.3 TRAINING SETTINGS OF PRDNET

A.3.1 HUBER LOSS FOR OUTLIER ROBUSTNESS

To accommodate the diverse nature of crystal property prediction tasks and improve training stability, PRDNet employs Huber loss (Meyer, 2021) for training.

The Huber loss combines the advantages of L2 loss for small errors and L1 loss for large errors:

$$\mathcal{L}_{\text{Huber}}(\hat{y}, y; \delta) = \begin{cases} \frac{1}{2}(\hat{y} - y)^2 & \text{if } |\hat{y} - y| \leq \delta \\ \delta|\hat{y} - y| - \frac{1}{2}\delta^2 & \text{otherwise} \end{cases} \quad (27)$$

where $\delta > 0$ is a hyperparameter that controls the transition point between quadratic and linear regimes. This formulation provides robustness against outliers while maintaining smooth gradients for small errors.

A.3.2 ADAMW WITH DECOUPLED WEIGHT DECAY

PRDNet employs the AdamW optimizer, which decouples weight decay from gradient-based updates:

$$\mathbf{m}_t = \beta_1 \mathbf{m}_{t-1} + (1 - \beta_1) \nabla_{\boldsymbol{\theta}} \mathcal{L}_t \quad (28)$$

$$\mathbf{v}_t = \beta_2 \mathbf{v}_{t-1} + (1 - \beta_2) (\nabla_{\boldsymbol{\theta}} \mathcal{L}_t)^2 \quad (29)$$

$$\hat{\mathbf{m}}_t = \frac{\mathbf{m}_t}{1 - \beta_1^t}, \quad \hat{\mathbf{v}}_t = \frac{\mathbf{v}_t}{1 - \beta_2^t} \quad (30)$$

$$\boldsymbol{\theta}_{t+1} = \boldsymbol{\theta}_t - \alpha_t \left(\frac{\hat{\mathbf{m}}_t}{\sqrt{\hat{\mathbf{v}}_t + \epsilon}} + \lambda \boldsymbol{\theta}_t \right) \quad (31)$$

where $\beta_1 = 0.9$, $\beta_2 = 0.999$, $\epsilon = 10^{-8}$, and λ is the weight decay coefficient.

A.3.3 COSINE ANNEALING WITH WARM RESTARTS

The learning rate schedule follows a cosine annealing pattern with periodic restarts:

$$\eta_t = \eta_{\min} + \frac{1}{2}(\eta_{\max} - \eta_{\min}) \left(1 + \cos \left(\frac{T_{\text{cur}}}{T_{\text{max}}} \pi \right) \right) \quad (32)$$

$$T_{\text{cur}} = t \bmod T_{\text{max}} \quad (33)$$

where T_{cur} is the current epoch within the restart cycle, T_{max} is the restart period, η_{\max} is the maximum learning rate, and η_{\min} is the minimum learning rate.

A.3.4 LAYER NORMALIZATION WITH LEARNABLE PARAMETERS

Layer normalization is applied to stabilize training:

$$\mu = \frac{1}{d} \sum_{i=1}^d x_i \quad (34)$$

$$\sigma^2 = \frac{1}{d} \sum_{i=1}^d (x_i - \mu)^2 \quad (35)$$

$$\text{LayerNorm}(\mathbf{x}) = \frac{\mathbf{x} - \mu}{\sqrt{\sigma^2 + \epsilon}} \odot \gamma + \beta \quad (36)$$

where γ and β are learnable scale and shift parameters.

B ABLATION STUDY

B.1 DIFFRACTION ABLATION

PRDNET-NoDiff removes diffraction integration entirely:

$$\mathbf{z}_{\text{nodiff}} = \text{MLP}_{\text{out}}(\mathbf{g}) \quad (37)$$

PRDNET-Full incorporates complete diffraction physics integration:

$$\mathbf{z}_{\text{fused}} = \text{MLP}_{\text{fusion}}([\mathbf{g} \oplus \mathbf{d}]) \quad (38)$$

$$\text{where } \mathbf{d} = \text{MLP}_{\text{diff}}([\mathbf{F}_{\text{real}} \oplus \mathbf{F}_{\text{imag}}]) \quad (39)$$

B.2 ATTENTION MECHANISM ABLATION

PRDNet-SingleHead uses single-head attention:

$$\mathbf{m}_{ij}^{\text{single}} = \text{Attention}(\mathbf{Q}_i, \mathbf{K}_j, \mathbf{V}_j, \mathbf{E}_{ij}) \quad (40)$$

PRDNet-Full employs multi-head attention:

$$\mathbf{m}_{ij}^{\text{multi}} = \bigoplus_{h=1}^H \text{Attention}^{(h)}(\mathbf{Q}_i^{(h)}, \mathbf{K}_j^{(h)}, \mathbf{V}_j^{(h)}, \mathbf{E}_{ij}^{(h)}) \quad (41)$$

B.3 RESIDUAL CONNECTION ABLATION

PRDNet-NoRes removes residual connections:

$$\mathbf{h}_i^{(l+1)} = \text{SiLU}(\text{BatchNorm}(\tilde{\mathbf{h}}_i^{(l+1)})) \quad (42)$$

PRDNet-Full uses residuals:

$$\mathbf{h}_i^{(l+1)} = \beta_i \odot \mathbf{h}_i^{(l)} + (1 - \beta_i) \odot \text{SiLU}(\text{BatchNorm}(\tilde{\mathbf{h}}_i^{(l+1)})) \quad (43)$$

B.4 EDGE FEATURE ABLATION

PRDNet-NoEdge excludes edge features from attention:

$$\alpha_{ij} = \frac{\mathbf{Q}_i \odot \mathbf{K}_j}{\sqrt{d}} \quad (44)$$

PRDNet-Full incorporates edge features:

$$\alpha_{ij} = \frac{(\mathbf{Q}_i \oplus \mathbf{Q}_i \oplus \mathbf{Q}_i) \odot (\mathbf{K}_i \oplus \mathbf{K}_j \oplus \mathbf{E}_{ij})}{\sqrt{3d}} \quad (45)$$

Table 5: Ablation study on the JARVIS-DFT. **Diff.** indicates whether the diffraction module is used, **MH** denotes single-head or multi-head attention, **Res.** specifies whether residual connections are applied during node attribute updates, and **EF** refers to the inclusion of edge features

Model	Diff.	MH	Res.	EF	Form. Energy	Bandgap	Bulk Modulus	Shear Modulus
Default	✓	✓	✓	✓	0.032	0.140	0.064	0.122
NoDiff	×	✓	✓	✓	0.055	0.333	0.287	0.291
SingleHead	✓	×	✓	✓	0.071	<u>0.291</u>	0.236	0.311
NoRes	✓	✓	×	✓	<u>0.048</u>	0.397	<u>0.201</u>	<u>0.237</u>
NoEdge	✓	✓	✓	×	0.083	0.412	0.289	0.341

Table 6: Ablation study on the MB. **Diff.** indicates whether the diffraction module is used, **MH** denotes single-head or multi-head attention, **Res.** specifies whether residual connections are applied during node attribute updates, and **EF** refers to the inclusion of edge features

Model	Diff.	MH	Res.	EF	Exfo. Energy	Form. Energy	Shear Modulus	Refractive Index
Default	✓	✓	✓	✓	0.038	0.019	0.058	0.242
NoDiff	×	✓	✓	✓	0.072	0.042	0.121	<u>0.297</u>
SingleHead	✓	×	✓	✓	0.121	<u>0.038</u>	<u>0.094</u>	0.298
NoRes	✓	✓	×	✓	<u>0.064</u>	<u>0.038</u>	0.101	0.311
NoEdge	✓	✓	✓	×	0.099	0.051	0.099	0.304

C CASE STUDY OF FORWARD PROPAGATION

To illustrate the complete PRDNet forward propagation process, we present a detailed case using a concrete example crystal structure. This section demonstrates how atomic-level information flows through the network to produce property predictions.

Input Crystal Structure Consider a simple cubic crystal structure \mathcal{X} :

- **Composition:** CaF₂
- **Unit cell:** 3 atoms with fractional coordinates
- **Lattice parameters:** $a = b = c = 5.46 \text{ \AA}$, $\alpha = \beta = \gamma = 90^\circ$
- **Space group:** Fm $\bar{3}$ m (face-centered cubic)

$$\text{Atom 1 (A): } Z_1 = 20, \quad \mathbf{r}_1 = (0.0, 0.0, 0.0) \quad (46)$$

$$\text{Atom 2 (B): } Z_2 = 9, \quad \mathbf{r}_2 = (0.25, 0.25, 0.25) \quad (47)$$

$$\text{Atom 3 (C): } Z_3 = 9, \quad \mathbf{r}_3 = (0.75, 0.75, 0.75) \quad (48)$$

where Z_i represents the atomic number and \mathbf{r}_i are fractional coordinates.

C.1 STEP 1: GRAPH CONSTRUCTION AND FEATURE INITIALIZATION

Neighbor Detection Using a cutoff radius $r_{\text{cut}} = 5.0 \text{ \AA}$ (for illustration), we identify atomic neighbors:

$$\mathcal{N}(1) = \{2, 3\} \quad (\text{A atom has 1 B + 1 C neighbor}) \quad (49)$$

$$\mathcal{N}(2) = \{1, 3\} \quad (\text{B atom has 1 A + 1 C neighbor}) \quad (50)$$

$$\mathcal{N}(3) = \{1, 2\} \quad (\text{C atom has 1 A + 1 B neighbor}) \quad (51)$$

Node Feature Initialization Atomic embeddings are initialized based on atomic numbers:

$$\mathbf{h}_1^{(0)} = \text{Embed}(Z_1 = 20) \in \mathbb{R}^{256} \quad (\text{Ca embedding}) \quad (52)$$

$$\mathbf{h}_2^{(0)} = \text{Embed}(Z_2 = 9) \in \mathbb{R}^{256} \quad (\text{F embedding}) \quad (53)$$

$$\mathbf{h}_3^{(0)} = \text{Embed}(Z_3 = 9) \in \mathbb{R}^{256} \quad (\text{F embedding}) \quad (54)$$

Edge Feature Construction For each atomic pair (i, j) , edge features encode geometric relationships:

$$d_{12} = \|\mathbf{r}_1 - \mathbf{r}_2\| = 2.36 \text{ \AA} \quad (55)$$

$$\mathbf{e}_{12} = \text{RBF}(d_{12}) \oplus \text{SBF}(\theta_{123}) \oplus d_{12} \in \mathbb{R}^{128} \quad (56)$$

where $\text{RBF}(\cdot)$ is the radial basis function and $\text{SBF}(\cdot)$ is the spherical basis function (Gasteiger et al.),.

C.2 STEP 2: MULTI-LAYER GRAPH CONVOLUTION

For each layer $l = 0, 1, \dots, L - 1$ (with $L = 6$ layers):

Multi-Head Attention For attention head $h = 1$ and atomic pair $(1, 2)$:

$$\mathbf{Q}_1^{(1)} = \mathbf{W}_Q^{(1)} \mathbf{h}_1^{(l)} \in \mathbb{R}^{32} \quad (\text{Query for atom 1}) \quad (57)$$

$$\mathbf{K}_1^{(1)} = \mathbf{W}_K^{(1)} \mathbf{h}_1^{(l)} \in \mathbb{R}^{32} \quad (\text{Key for atom 1}) \quad (58)$$

$$\mathbf{K}_2^{(1)} = \mathbf{W}_K^{(1)} \mathbf{h}_2^{(l)} \in \mathbb{R}^{32} \quad (\text{Key for atom 2}) \quad (59)$$

$$\mathbf{V}_1^{(1)} = \mathbf{W}_V^{(1)} \mathbf{h}_1^{(l)} \in \mathbb{R}^{32} \quad (\text{Value for atom 1}) \quad (60)$$

$$\mathbf{V}_2^{(1)} = \mathbf{W}_V^{(1)} \mathbf{h}_2^{(l)} \in \mathbb{R}^{32} \quad (\text{Value for atom 2}) \quad (61)$$

$$\mathbf{E}_{12}^{(1)} = \mathbf{W}_E^{(1)} \mathbf{e}_{12} \in \mathbb{R}^{32} \quad (\text{Edge projection}) \quad (62)$$

Attention Score Calculation

$$\mathbf{q}_{12}^{(1)} = \mathbf{Q}_1^{(1)} \oplus \mathbf{Q}_1^{(1)} \oplus \mathbf{Q}_1^{(1)} \in \mathbb{R}^{96} \quad (63)$$

$$\mathbf{k}_{12}^{(1)} = \mathbf{K}_1^{(1)} \oplus \mathbf{K}_2^{(1)} \oplus \mathbf{E}_{12}^{(1)} \in \mathbb{R}^{96} \quad (64)$$

$$\boldsymbol{\alpha}_{12}^{(1)} = \frac{\mathbf{q}_{12}^{(1)} \odot \mathbf{k}_{12}^{(1)}}{\sqrt{96}} \in \mathbb{R}^{96} \quad (65)$$

Message Aggregation

$$\mathbf{m}_{12}^{(1)} = \mathbf{W}_{\text{msg}} (\mathbf{V}_1^{(1)} \oplus \mathbf{V}_2^{(1)} \oplus \mathbf{E}_{12}^{(1)}) \odot \sigma(\boldsymbol{\alpha}_{12}^{(1)}) \quad (66)$$

$$\mathbf{m}_1^{\text{agg}} = \mathbf{m}_{12}^{(1)} \oplus \mathbf{m}_{13}^{(1)} \oplus \dots \oplus \mathbf{m}_{12}^{(H)} \oplus \mathbf{m}_{13}^{(H)} \quad (67)$$

Node Updating

$$\mathbf{h}_1^{(l+1)} = \beta_i \odot \mathbf{h}_i^{(l)} + (1 - \beta_i) \odot \text{SiLU}(\text{BatchNorm}(\mathbf{W}_{\text{concat}} \mathbf{m}_1^{\text{agg}})) \quad (68)$$

C.3 STEP 3: PHYSICS INTEGRATION - DIFFRACTION MODULE

Learnable Form Factor After L graph convolution layers, compute atomic form factors:

$$f_1(\mathcal{H}) = \text{MLP}_{\text{form}}(\mathbf{h}_1^{(L)}) = (2.34, \dots) \quad (\text{Ca form factor}) \quad (69)$$

$$f_2(\mathcal{H}) = \text{MLP}_{\text{form}}(\mathbf{h}_2^{(L)}) = (1.87, \dots) \quad (\text{F form factor}) \quad (70)$$

$$f_3(\mathcal{H}) = \text{MLP}_{\text{form}}(\mathbf{h}_3^{(L)}) = (1.91, \dots) \quad (\text{F form factor}) \quad (71)$$

Structure Factor For selected Miller indices, e.g., $(h, k, l) = (1, 0, 0) \in \mathcal{H}$:

$$F_{100} = \sum_{j=1}^3 f_j \exp(2\pi i(1 \cdot x_j + 0 \cdot y_j + 0 \cdot z_j)) \quad (72)$$

$$= f_1 \exp(2\pi i \cdot 0) + f_2 \exp(2\pi i \cdot 0.25) + f_3 \exp(2\pi i \cdot 0.75) \quad (73)$$

$$= 2.34 + 1.87e^{i\pi/2} + 1.91e^{i3\pi/2} \quad (74)$$

$$= 2.34 + 1.87i - 1.91i = 2.34 + (-0.04)i \quad (75)$$

where i is the imaginary unit.

Diffraction Feature Vector For $N_{\text{hkl}} = 300$ Miller indices:

$$\mathbf{F}_{\text{real}} = [\text{Re}(F_{100}), \text{Re}(F_{010}), \dots] = [2.34, 1.23, \dots] \quad (76)$$

$$\mathbf{F}_{\text{imag}} = [\text{Im}(F_{100}), \text{Im}(F_{010}), \dots] = [-0.04, 0.87, \dots] \quad (77)$$

$$\mathbf{F}_{\text{concat}} = [\mathbf{F}_{\text{real}} \oplus \mathbf{F}_{\text{imag}}] \quad (78)$$

C.4 STEP 4: MULTI-MODAL FUSION

Graph Feature Pooling

$$\mathbf{g} = \frac{1}{3}(\mathbf{h}_1^{(L)} + \mathbf{h}_2^{(L)} + \mathbf{h}_3^{(L)}) \in \mathbb{R}^{256} \quad (\text{Mean pooling}) \quad (79)$$

Diffraction Processing

$$\mathbf{d} = \text{MLP}_{\text{diff}}(\mathbf{F}_{\text{concat}}) \in \mathbb{R}^{256} \quad (\text{Diffraction features}) \quad (80)$$

Feature Fusion and Prediction

$$\mathbf{z}_{\text{fused}} = \text{MLP}_{\text{fusion}}([\mathbf{g} \oplus \mathbf{d}]) \in \mathbb{R}^{128} \quad (81)$$

$$\hat{y} = \text{MLP}_{\text{out}}(\mathbf{z}_{\text{fused}}) = -2.47 \text{ eV/atom} \quad (82)$$

The final prediction $\hat{y} = -2.47 \text{ eV/atom}$ represents the formation energy of the CaF_2 crystal structure.

D HYPERPARAMETERS

We provide a detailed hyperparameter settings used in the benchmark models for fair comparison.

- **CGCNN:** We use the released implementation from the official repo, with 300 training epochs, batch size of 64, an initial learning rate of 0.001 scheduled by OneCycleLR, and weight decay set to 1×10^{-5} . The graph encoder uses 256 atom features with 6 convolutional layers, followed by a fully connected network with hidden dimension 128. Mean squared error (MSE) loss is used for regression and negative log-likelihood (NLL) loss with log-softmax for classification.
- **SchNet:** We implement SchNet in SchNetPack and the default training script, with 500 training epochs, batch size of 64. The graph was constructed with a neighbor cutoff of 8 Å and Gaussian radial basis functions with 80 bases. The graph encoder used hidden size of 128 and 3 interaction blocks. Optimization is performed with AdamW using a learning rate of 1×10^{-3} and weight decay of 1×10^{-5} . Training is run with checkpointing on validation loss, without a learning rate scheduler. MSE loss is used for training regression tasks and the cross entropy loss for classification task.

Algorithm 1 PRDNet Forward Propagation

Require: Crystal structure graph $\mathcal{G} = (\mathcal{V}, \mathcal{E})$, atomic positions $\{\mathbf{r}_i\}_{i=1}^N$, lattice parameters

Ensure: Property prediction $\hat{y} \in \mathbb{R}$

Initialize: Node features $\mathbf{h}_i^{(0)} = \text{Embed}(Z_i)$ for $i = 1, \dots, N$

Compute: Edge features $\mathbf{e}_{ij} = \text{RBF}(d_{ij}) \oplus \text{SBF}(\theta_{ijk}) \oplus d_{ij}$

for $l = 0$ to $L - 1$ **do**

for each attention head $h = 1$ to H **do**

 Compute projections: $\mathbf{Q}_i^{(h)}, \mathbf{K}_j^{(h)}, \mathbf{V}_j^{(h)}, \mathbf{E}_{ij}^{(h)}$ (Eq. 8)

 Calculate attention: $\alpha_{ij}^{(h)}$ (Eq. 9)

 Compute messages: $\mathbf{m}_{ij}^{(h)}$ (Eq. 10)

end for

 Aggregate multi-head messages: $\mathbf{m}_i^{\text{agg}}$ (Eq. 11)

 Apply linear projection: $\tilde{\mathbf{h}}_i^{(l+1)} = \mathbf{W}_{\text{concat}} \mathbf{m}_i^{\text{agg}}$

 Normalize and activate: $\mathbf{h}_i^{(l+1)} = \beta_i \odot \tilde{\mathbf{h}}_i^{(l+1)} + (1 - \beta_i) \odot \text{SiLU}(\text{BatchNorm}(\tilde{\mathbf{h}}_i^{(l+1)}))$

end for

Physics Integration:

 Compute form factors: $f_j(\mathcal{H}) = \text{MLP}_{\text{form}}(\mathbf{h}_j^{(L)})$ for $j = 1, \dots, N$

 Calculate structure factors: $F_{hkl} = \sum_{j=1}^N f_j \exp(2\pi i \mathbf{h} \cdot \mathbf{r}_j)$ for $(h, k, l) \in \mathcal{H}, f_j \in f_j(\mathcal{H})$

 Construct diffraction map: $\mathbf{F}_{\text{concat}} = [\text{Re}(\mathbf{F}) \oplus \text{Im}(\mathbf{F})]$

Feature Fusion:

 Pooling: $\mathbf{g} = \text{MeanPool}(\{\mathbf{h}_i^{(L)}\}_{i=1}^N)$

 Process diffraction: $\mathbf{d} = \text{MLP}_{\text{diff}}(\mathbf{F}_{\text{concat}})$

 Fuse modalities: $\mathbf{z}_{\text{fused}} = \text{MLP}_{\text{fusion}}([\mathbf{g} \oplus \mathbf{d}])$

Final Prediction: $\hat{y} = \text{MLP}_{\text{out}}(\mathbf{z}_{\text{fused}})$

return \hat{y}

- **MEGNet:** We adopted the MatGL implementation and the default training script. Crystal structures are converted into graphs with a neighbor cutoff of 4 Å and Gaussian radial basis expansion of 100 centers (width = 0.5). The embedding dimensions are 16 for nodes, 100 for edges, and 2 for global states. The network contains 3 MEGNet blocks with hidden sizes of (64, 32) in the input MLP, (64, 64, 32) in the convolutional MLP, and (32, 16) in the output MLP. The softplus2 is used as activation function. The model is trained with batch size 64 for up to 1000 epochs using Adam optimizer, mean squared error loss, and early stopping with patience of 500.
- **GATGNN:** We used the released implementation with graph attention layers. The network contains 4 GAT layers, each with 128 neurons and 4 attention heads. The default unpooling strategy is fixed-cluster. We train with a batch size of 64, learning rate of 1×10^{-3} , and AdamW optimizer with weight decay 1×10^{-4} . A MultiStepLR scheduler is applied with milestones at 150 and 250 epochs and decay factor 0.3. Training runs for up to 1000 epochs with SmoothL1 loss for regression tasks (CrossEntropyLoss for classification) and early stopping with patience of 150.
- **MatFormer:** We use the released implementation from the official repo, with 500 training epochs, batch size of 512, an initial learning rate of 0.001 scheduled by OneCycleLR with 2000 warmup steps, and weight decay set to 1×10^{-5} . The Matformer encoder uses 128 node features with 5 convolutional layers and 4 attention heads per layer, followed by a fully connected network with hidden dimension 128. The model employs 92-dimensional atom input features, 128-dimensional edge features, and uses k-nearest neighbor strategy with cutoff distance of 8.0 Å and maximum 12 neighbors. MSE loss is used for regression and NLL loss with log-softmax for classification.
- **CrystalFormer:** We use the released implementation from the official repo, with 500 training epochs, batch size of 256, an initial learning rate of 0.0005 scheduled by inverse square root without warmup, and weight decay set to 1×10^{-5} . The CrystalFormer encoder uses 128 model dimensions with 4 transformer layers, 8 attention heads, and a feed-forward dimension of 512. The model employs adaptive cutoff with sigma value of -3.5, lattice range of 2, and uses both real and reciprocal space representations with Gaussian basis functions. Position encoding is applied with distance-based features (64 dimensions) and scale factors of 1.4 for real space and 2.2 for

reciprocal space. L1 loss is used for regression tasks and cross-entropy loss for classification tasks, with average pooling for graph-level predictions.

- **CrystalFramer:** We use the released implementation from the official repo, with 500 training epochs, batch size of 256, an initial learning rate of 0.0005 scheduled by inverse square root without warmup, and weight decay set to 1×10^{-5} . The CrystalFramer encoder uses 128 model dimensions with 4 transformer layers, 8 attention heads, and a feed-forward dimension of 512. The model employs adaptive cutoff with sigma value of -3.5, lattice range of 2, and uses real space representations with Gaussian basis functions. Position encoding is applied with distance-based features (64 dimensions) and angle-based features (64 dimensions), with scale factors of 1.4 for real space and 2.2 for reciprocal space. L1 loss is used for regression tasks and cross-entropy loss for classification tasks, with average pooling for graph-level predictions.
- **eComFormer:** We use the released implementation from the official repo, with 500 training epochs, batch size of 512, an initial learning rate of 0.001 scheduled by OneCycleLR with 2000 warmup steps, and weight decay set to 0. The eComformer encoder uses 256 node features with 3 convolutional layers and 1 attention head per layer, followed by a fully connected network with hidden dimension 256. The model employs 92-dimensional atom input features, 256-dimensional edge features, and uses k-nearest neighbor strategy with cutoff distance of 8.0 Å and maximum 12 neighbors. The architecture incorporates equivariant updates with second-order representations and uses radial basis functions with range from -4.0 to 0.0 for edge encoding. MSE loss is used for regression and cross-entropy loss for classification.

E BACKGROUND OF PREDICTION TARGETS

- **Formation Energy.** The formation energy (Gillan, 1989) quantifies the thermodynamic stability of a material and is defined as the energy required to form a compound from its constituent elements in their reference states.

$$E_{\text{form}} = E_{\text{tot}} - \sum_i n_i \mu_i, \quad (83)$$

where E_{tot} is the total energy of the compound, n_i is the number of atoms of element i in the formula unit, and μ_i is the chemical potential (reference energy) of element i . A negative formation energy indicates that the compound is thermodynamically favorable with respect to decomposition into its elements. The unit we used is eV/atom, obtained by dividing the total energy by the number of atoms.

- **Band Gap and Metal/Non-metal Classification** The band gap E_g (Zaanen et al., 1985) is a fundamental electronic property defined as the energy difference between the conduction band minimum (CBM) and the valence band maximum (VBM):

$$E_g = E_{\text{CBM}} - E_{\text{VBM}}. \quad (84)$$

The unit we used is eV. Materials with $E_g > 0$ are classified as semiconductors or insulators depending on the magnitude of the gap, whereas those with $E_g = 0$ are considered metallic. Hence, the band gap also serves as a basis for the **metal/non-metal classification** of materials.

- **Bulk Modulus.** The bulk modulus B (Makishima & Mackenzie, 1975) represents resistance to uniform compression and is defined as:

$$B = -V \left(\frac{\partial P}{\partial V} \right), \quad (85)$$

where V is the volume and P is the pressure.

- **Shear Modulus.** The shear modulus G (Makishima & Mackenzie, 1975) characterizes the material’s response to shear stress and is calculated from the elastic stiffness tensor or averaged using the Voigt-Reuss-Hill approximation.

$$G = \frac{\tau}{\gamma}, \quad (86)$$

where τ is the shear stress and γ is the shear strain. The unit we used is GPa, and we applied a logarithmic transformation to its values for comparison with the leaderboard results.

- **Young's Modulus.** The Young's modulus E (Kalra et al., 2016) measures the stiffness under uniaxial stress. For isotropic materials, it is calculated as:

$$E = \frac{9BG}{3B + G}. \quad (87)$$

The unit we used is GPa, and we applied a logarithmic transformation to its values for comparison with the leaderboard results.

- **Exfoliation Energy.** The exfoliation energy (Jung et al., 2018) quantifies the energy cost to isolate a single atomic layer from a bulk layered material, which is critical in evaluating the feasibility of two-dimensional material synthesis. It is defined as:

$$E_{\text{exf}} = \frac{E_{\text{mono}} - E_{\text{bulk}}/N}{A}, \quad (88)$$

where E_{mono} is the energy of the isolated monolayer, E_{bulk} is the total energy of the bulk material containing N layers, and A is the surface area of the monolayer. A lower exfoliation energy indicates easier mechanical or chemical exfoliation. The unit we used is meV/atom, obtained by dividing the exfoliation energy by the number of atoms.